

Superconductivity, charge orderings, magnetism, and their phase separations in the ground state of lattice models of superconductor with very short coherence length

Konrad Jerzy Kapcia*

*Electron States of Solids Division, Faculty of Physics,**Adam Mickiewicz University in Poznań, ul. Umultowska 85, 61-614 Poznań, Poland*

(Dated: December 8, 2014)

We present the ground state results for lattice models of superconductor (SC) with extremely short coherence length, which also involve the interplay with charge (CO) and (anti-)ferromagnetic orderings. Our preliminary results at zero-temperature (derived by means of the variational approach which treats the on-site interaction term exactly and the intersite interactions within the mean-field approximation, exact in $d \rightarrow +\infty$), yields that the SC phase can coexist with the CO or magnetic (M) phases in states with electron phase separation (PS:SC/CO and PS:SC/M, respectively).

PACS numbers:

71.10.Fd — Lattice fermion models (Hubbard model, etc.)

74.20.-z — Theories and models of superconducting state

74.25.Dw — Superconductivity phase diagrams

64.75.Gh — Phase separation and segregation in model systems (hard spheres, Lennard-Jones, etc.)

71.10.Hf — Non-Fermi-liquid ground states, electron phase diagrams and phase transitions in model systems

Keywords: extended Hubbard model, atomic limit, phase separation, superconductivity, magnetism, charge-order, pair hopping, phase diagrams

I. INTRODUCTION

The interplay and competition between superconductivity (SC) and other electron orderings, such as charge orderings (CO) or various magnetic (M) orderings is currently under intense investigations in broad range of materials including cuprates, bismutates, iron-pnictides, organic conductors and heavy-fermion systems (for review see e.g. Refs. [1–14] and references therein). Moreover, the phase separation (PS) has been evidenced (by various microscopy techniques such as STM, MFM, etc.) in some of materials from the groups mentioned previously, especially in iron-pnictides (PS with M), bismutates (PS with CO) and cuprates.

In this paper we study a simplified model which can pertain to that problem. The effective model considered has a form of single-band extended Hubbard model with pair hopping at the atomic limit ($t = 0$) [4–17]:

$$\begin{aligned} \hat{H} = & U \sum_i \hat{n}_{i\uparrow} \hat{n}_{i\downarrow} - \mu \sum_i \hat{n}_i \\ & - I \sum_{\langle i,j \rangle} (\hat{\rho}_i^+ \hat{\rho}_j^- + \hat{\rho}_j^+ \hat{\rho}_i^-) + \frac{W}{2} \sum_{\langle i,j \rangle} \hat{n}_i \hat{n}_j \\ & - 2J^z \sum_{\langle i,j \rangle} \hat{s}_i^z \hat{s}_j^z - J^{xy} \sum_{\langle i,j \rangle} (\hat{s}_i^+ \hat{s}_j^- + \hat{s}_j^+ \hat{s}_i^-), \end{aligned} \quad (1)$$

where $\hat{n}_{i\sigma} = \hat{c}_{i\sigma}^+ \hat{c}_{i\sigma}$, $\hat{n}_i = \sum_{\sigma} \hat{n}_{i\sigma}$, $\hat{\rho}_i^+ = (\hat{\rho}_i^-)^\dagger = \hat{c}_{i\uparrow}^+ \hat{c}_{i\downarrow}^+$, $\hat{s}_i^z = (1/2)(\hat{n}_{i\uparrow} - \hat{n}_{i\downarrow})$ and $\hat{s}_i^+ = (\hat{s}_i^-)^\dagger = \hat{c}_{i\uparrow}^+ \hat{c}_{i\downarrow}$. $\hat{c}_{i\sigma}^+$ and $\hat{c}_{i\sigma}$ denote the creation and annihilation operators, respectively, of an electron with spin σ ($\sigma = \uparrow, \downarrow$) at site

i , which fulfil standard anticommutation relations for fermionic operators. μ is the chemical potential. The nearest-neighbors interactions U , I , W , J^z , J^{xy} are effective model parameters and are assumed to include all the possible renormalizations and contributions like those coming from the strong electron-phonon coupling or from the coupling between electrons and other electronic subsystems in solid or chemical complexes.

The analysis of the ground state of model (1) has been performed by means of a variational approach (VA) in the grand canonical ensemble [6–14], which treats on-site U term exactly and the intersite interactions within the mean-field approximation (MFA). The MFA is a rigorous treatment of the intersite terms in the limit of infinite dimensions $d \rightarrow +\infty$ (or large coordination number z); thus, the result obtained in this paper for model (1) are also exact in the limit $d \rightarrow +\infty$. This approach allows us to calculate the grand canonical potential per site $\omega = \langle \hat{H} \rangle / L$ and the (free) energy per site $E = \langle \hat{H} + \mu \sum_i \hat{n}_i \rangle / L = \omega + \mu n$ (at $T = 0$, L is a number of lattice sites). $\langle \hat{A} \rangle$ is an average value of operator \hat{A} .

Let us introduce the following mean-field order parameters:

$$n_{\vec{q}} = \frac{1}{L} \sum_i \exp(i\vec{q} \cdot \vec{r}_i) \langle \hat{n}_i \rangle, \quad (2)$$

$$\Delta_{\vec{q}} = \frac{1}{L} \sum_i \exp(i\vec{q} \cdot \vec{r}_i) \langle \hat{\rho}_i^- \rangle, \quad (3)$$

$$m_{\vec{q}}^\alpha = \frac{1}{L} \sum_i \exp(i\vec{q} \cdot \vec{r}_i) \langle \hat{s}_i^\alpha \rangle, \quad (4)$$

where \vec{r}_i determines the location of i -site and $\alpha = z, \pm$ ($m_{\vec{q}}^+ = (m_{\vec{q}}^-)^*$). We restrict ourselves only to a case of two sublattice orderings on the alternate lattices, i.e. $\vec{q} = \vec{0}, \vec{Q}$, where \vec{Q} is a half of the smallest reciprocal

* e-mail:konrad.kapcia@amu.edu.pl

lattice vector. $n \equiv n_{\bar{0}}$ is an electron concentration in the system. In the charge-ordered (CO) phase $n_{\bar{Q}} \neq 0$. Model (1) exhibits a symmetry between $I > 0$ (SC with s -pairing, $\Delta_{\bar{0}} \neq 0$) and $I < 0$ (SC with η -pairing, $\Delta_{\bar{Q}} \neq 0$) cases. Similar symmetry occurs for spin orderings in both direction ($\alpha = z, \pm$) between ferro- (with $m_{\bar{0}}^{\alpha} \neq 0$) and antiferro- (with $m_{\bar{Q}}^{\alpha} \neq 0$) magnetic (M) phases. Notice that for general case of both J^{xy} and J^z nonzero that symmetry is valid only for VA results. The boundary between M phases with orderings in z -direction and xy -direction is for $|J^{xy}/J^z| = 1$ (in VA). Thus we define $|J| = \text{Max}\{|J^z|, |J^{xy}|\}$. Both symmetries in the above-mentioned discussion are for model (1) on the alternate lattices (i.e. lattices, which consist of two interpenetrating lattices). In the presence of finite single electron hopping $t \neq 0$, both of above-mentioned symmetries are broken in the general case [18–30], but the detailed discussion of effects of $t \neq 0$ is beyond the scope of this publication. Moreover, because of the particle-hole symmetry of model (1) the phase diagrams obtained are symmetric with respect to $\bar{\mu} = 0$ ($\bar{\mu} = \mu - U/2 - W_0$, $W_0 = zW$) as well as $n = 1$. The equations for energies of phases and states for $n \geq 1$ can be obtained using the relation $\bar{E}(2-n) = E(n) + (U + 2W_0)(1-n)$, where $E(n)$ is the energy for $n \leq 1$ (Eqs. (10)–(15) and (17) below) and $\bar{E}(n)$ is the energy for $n \geq 1$. For order parameters the relation $\bar{\psi}(2-n) = -\psi^*(n)$ is fulfilled ($n \neq 1$), where $\psi = \Delta_{\bar{q}}, m_{\bar{q}}^{\alpha}, n_{\bar{Q}} (n_{\bar{Q}} = n_{\bar{Q}}^*, (m_{\bar{q}}^z)^* = m_{\bar{q}}^z)$.

The PS state (macroscopic separation) is a state in which two domains with different electron concentrations (n_+ and n_-) exist in the system (coexistence of two homogeneous phases). The energies of the PS states are calculated from minimization of the expression

$$E_{\text{PS}}(n_+, n_-) = mE_+(n_+) + (1-m)E_-(n_-), \quad (5)$$

where $E_{\pm}(n_{\pm})$ are values of the energy of two separating phases at n_{\pm} corresponding to the lowest homogeneous solution for a given phase, m is the fraction of the system with charge density n_+ , and $mn_+ + (1-m)n_- = n$ [8, 31–34].

In this paper we focus on the ground state of model (1) in two cases: (i) $J = 0$ and $U \leq 0$ – Section II A; as well as (ii) $W = 0$ – Section II B. Names of transition orders used are consistent with our earlier works [7–14, 33–36]. In particular, a transition between a homogeneous phase and the PS state is symbolically named as a “third-order” transition.

II. THE GROUND STATE RESULTS ($T = 0$)

A. Superconductivity and charge orderings ($J = 0$ and $U \leq 0$)

For any $U \leq 0$ and $J^z, J^{xy} = 0$ the ground state phase diagrams of model (1) are shown in Fig. 1. Fig. 1(a) is a

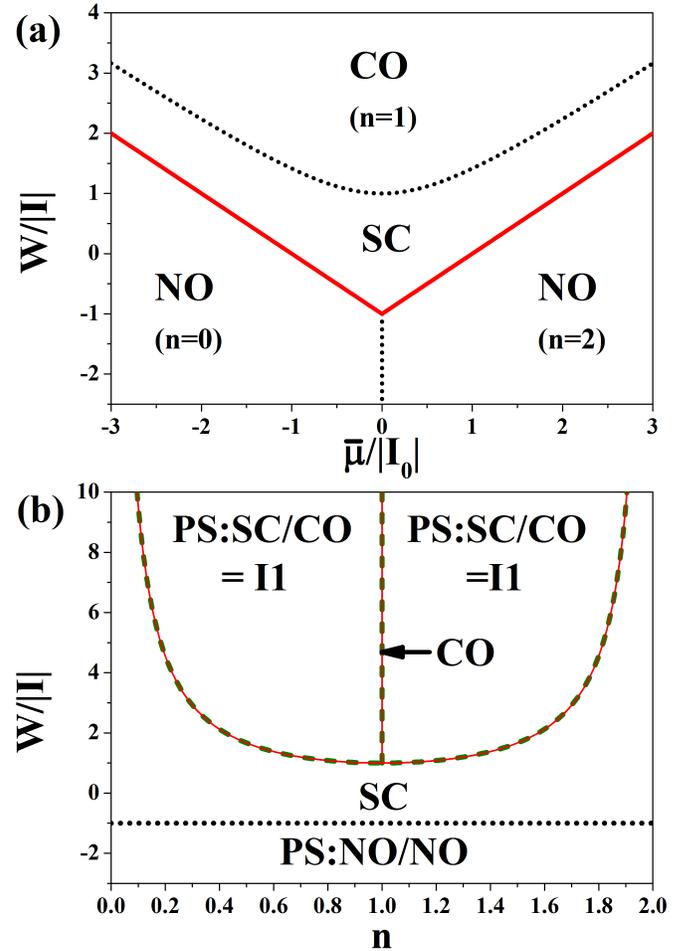


FIG. 1. Ground state diagram for $U \leq 0$ and $J = 0$ as a function of μ (a) and as a function of n (b). Dotted, solid and dashed lines denote first-order, second-order and “third-order” transitions, respectively. Details in text.

result of comparison of the grand canonical potentials of particular phases, which are as following:

$$\omega_{\text{NO}}^a = 0, \quad (n = 0) \quad (6)$$

$$\omega_{\text{NO}}^b = -2\bar{\mu}, \quad (n = 2) \quad (7)$$

$$\omega_{\text{CO}} = -\bar{\mu} - W_0, \quad (n = 1, n_{\bar{Q}} = 1) \quad (8)$$

$$\omega_{\text{SC}} = -\frac{(\bar{\mu} + |I_0| + W_0)^2}{2(|I_0| + W_0)}, \quad \left(n = 1 + \frac{\bar{\mu}}{|I_0| + W_0} \right) \quad (9)$$

where $I_0 = zI$ and $W_0 = zW$. The second-order NO–SC phase boundary is determined by $W_0/I_0 = |\bar{\mu}/I_0| - 1$ (n and $\Delta_{\bar{q}}$ are continuous). The first-order SC–CO transition occurs for $(W_0/I_0)^2 = (\bar{\mu}/I_0)^2 + 1$, at which $\Delta_{\bar{q}}$ and $n_{\bar{Q}}$ are discontinuous. n changes (discontinuously, except $\bar{\mu} = 0$) from $n_{\text{SC}} = 1 \mp \sqrt{(W_0 - |I_0|)/(W_0 + |I_0|)}$ in the SC phase (for $n \leq 1$, respectively) to $n_{\text{CO}} = 1$ in the CO phase. A first-order NO–NO transition occurs for $\bar{\mu} = 0$ and $W/|I| < -1$.

As a function of n the energies of the particular homo-

geneous phases are as follows (for $n \leq 1$):

$$E_{\text{NO}} = \frac{1}{2}(U + W_0 n)n, \quad (10)$$

$$E_{\text{SC}} = \frac{1}{2}[(U + 2W_0)n - (|I_0| + W_0)n(2 - n)], \quad (11)$$

$$E_{\text{CO}} = \frac{1}{2}Un, \quad (n_{\bar{Q}} = n) \quad (12)$$

$$E_{\text{II}} = E_{\text{SC}} + \quad (13)$$

$$- \frac{1}{2} \left[\sqrt{W_0 + |I_0|}(1 - n) - \sqrt{W_0 - |I_0|} \right]^2,$$

where we also consider the mixed phase (II) in which three order parameters: $n_{\bar{Q}}$, $\Delta_{\bar{Q}}$ and $\Delta_{\bar{Q}}$ are non-zero (microscopic coexistence of SC and CO). In the SC phase: $|\Delta_{\bar{Q}}^2|_{\bar{Q}} = \frac{1}{4}n(2 - n)$, $|\Delta_{\bar{Q}}^2|_{\bar{Q}/\bar{\sigma}} = 0$ (for $I \geq 0$, respectively), and $n_{\bar{Q}} = 0$. For the II phase (in the range of its definiteness and $n \leq 1$) one obtains: $|\Delta_{\bar{Q}}^2|_{\bar{Q}} = \frac{1}{4} \left\{ n(2 - n) - \left[1 + (n - 1)\sqrt{\frac{W_0 + |I_0|}{W_0 - |I_0|}} \right] \right\}$, $|\Delta_{\bar{Q}}^2|_{\bar{Q}/\bar{\sigma}} = \frac{1}{4}(n - 1) \left[1 - n - \sqrt{\frac{W_0 - |I_0|}{W_0 + |I_0|}} \right]$ (for $I \geq 0$, respectively), and $n_{\bar{Q}}^2 = 1 + (n - 1)^2 + (n - 1)\frac{2W_0}{\sqrt{W_0^2 - I_0^2}}$. In this phase $\bar{\mu}_{\text{II}} = \mp \sqrt{W_0^2 - I_0^2}$ (for $n \leq 1$, respectively), what implies that the II phase can occur only at the SC–CO boundary in Fig. 1(a). Notice that in the II phase the $\bar{\mu}$ -dependences of n , $n_{\bar{Q}}$, $\Delta_{\bar{Q}}$ and $\Delta_{\bar{Q}}$ are indefinite, whereas in the SC phase it can be easily obtained by using Eq. (9) (i.e. $n = n(\bar{\mu})$).

The first-order boundaries (for fixed $\bar{\mu}$) can be associated with the existence of the PS states in define ranges of n (for fixed n). In our model two such states can occur: (i) PS:SC/CO with concentrations in domains: $n_{\text{SC}} = 1 \mp \sqrt{(W_0 - |I_0|)/(W_0 + |I_0|)}$ ($n \leq 1$, respectively) and $n_{\text{CO}} = 1$ as well as (ii) PS:NO/NO with concentrations in domains: $n_{\text{NO}}^a = 0$ and $n_{\text{NO}}^b = 2$. Using (5) and (10)–(12) one obtains (for $n \leq 1$):

$$E_{\text{PS:SC/CO}} = \frac{1}{2}Un + (1 - n) \left[\sqrt{W_0^2 - I_0^2} - W_0 \right], \quad (14)$$

$$E_{\text{PS:NO/NO}} = \left(\frac{1}{2}U + W_0 \right) n. \quad (15)$$

Comparing energies (10)–(15) we obtain the diagram shown in Fig. 1(b). The II phase and the PS:SC/CO state are degenerated in the whole ranges of their occurrences, but at $T > 0$ this degeneration is removed and only the PS:SC/CO state exists [13]. The SC–II and II–CO transitions are second-order, whereas the SC–PS:SC/CO and PS:SC/CO–CO transitions are “third-order”. At the PS:NO/NO–SC transition the sizes of domains change discontinuously as well as the occurring orderings change; thus, we classified this transition as first-order rather than “third-order” (cf. the definitions of phase boundaries in [33–36]). Notice that in all phases and states above there are no single occupied sites ($\sum_i \langle |\hat{s}_i^z| \rangle / L = 0$ and $m_{\bar{q}}^\alpha = 0$) and all electrons are locally paired. The results obtained are in agreement with those for $U \rightarrow -\infty$ (VA, fixed n) [32, 37]. In that limit the results derived by RPA approach for $d = 1, 2, 3$ lattices

[4, 38, 39] are consistent with Fig. 1(b), but for these dimensions the critical concentration $n_c \neq 0$ exist that for $0 < n < n_c$ only the SC phase exists (for any $W/|I| > 0$, here: $n, n_c < 1$). The PS:SC/CO state for $W > 0$ has not been considered in [4, 37–39].

B. Superconductivity and magnetism ($W = 0$)

For $W = 0$ and $T = 0$ the phase diagrams of model (1) are shown in Fig. 2. On the diagram as a function of $\bar{\mu}$ (shown in Fig. 2(a)) the NO (with $n = 0$ or $n = 2$), SC, and M phases occurs, whose grand potentials are given by (6), (7), (9) (for $W_0 = 0$), and

$$\omega_{\text{M}} = -\bar{\mu} - U/2 - |J_0|/2 \quad (n = 1, m_{\bar{q}}^\alpha = 1/2), \quad (16)$$

respectively ($|J_0| = z|J|$). The first-order SC–M boundary is located at $(U + |J_0|)/|I_0| = (\bar{\mu}/I_0)^2 + 1$. The SC–NO transitions at $|\bar{\mu}/I_0| = 1$ are second-order.

Similarly as in previous section we derived the energies of particular phases and possible PS states for fixed n . For the M phase we obtain ($n \leq 1$):

$$E_{\text{M}} = -\frac{1}{2}|J_0|n^2, \quad (m_{\bar{q}}^\alpha = n/2) \quad (17)$$

whereas the energies: (i) $E_{\text{PS:SC/M}}$ of the PS:SC/M state with concentrations in domains: $n_{\text{SC}} = 1 \mp \sqrt{(U + |J_0|)/|I_0| - 1}$ (for $n \leq 1$) and $n_{\text{M}} = 1$; (ii) $E_{\text{PS:NO/M}}$ of the PS:NO/M state with concentrations in domains: $n_{\text{NO}}^a = 0$ ($n < 1$) or $n_{\text{NO}}^b = 2$ ($n < 1$) and $n_{\text{M}} = 1$ as well as E_{SC} for the SC phase can be derived from (5) and (10), (11) (with $W_0 = 0$) and (17).

The resulting diagram as a function of n is shown in Fig. 2(b). Notice that in the M phase: $\mu_{\text{M}} = -|J_0|n$ and $\frac{\partial \mu}{\partial n} < 0$ for $n < 1$. Thus the M phase occurs only for $n = 1$ and $(U + |J_0|)/|I_0| > 1$ (cf. Refs. [12, 40–42]). The mixed phase (I2) in which order parameters $\Delta_{\bar{q}}$ and $m_{\bar{q}}^\alpha$ are non-zero (microscopic coexistence of SC and M) does not exist in any range of $\bar{\mu}$ and n . The PS:SC/M–PS:NO/M is second-order transition between two PS states, because in the SC domain $\Delta_{\bar{q}}$ goes continuously to zero, whereas in the other domain (M) $m_{\bar{q}}^\alpha \neq 0$ and it changes continuously [33–36]. The PS:SC/M–M and PS:NO/M–M transitions are “third-order” ones.

For $J = 0$ the M phase reduces into the NO’ phase with $\omega_{\text{NO}'} = -\bar{\mu} - U/2$ ($n = 1$) and $E_{\text{NO}'}(n) = 0$ (for $n < 1$) [8–11], and the PS states on Fig. 2(b) change into PS’:SC/NO’ and PS’:NO/NO’ states, whose energies can be derived from (5) analogously. The energies of this NO’ phase and the PS’:NO/NO’ state are equal at $T = 0$, but at $T > 0$ the PS’ does not occur. In such a case, the PS’:SC/NO’–PS’:NO/NO’ is second-order transition between two PS states [33–36], whereas the PS’:SC/NO’–NO’ transition is “third-order”.

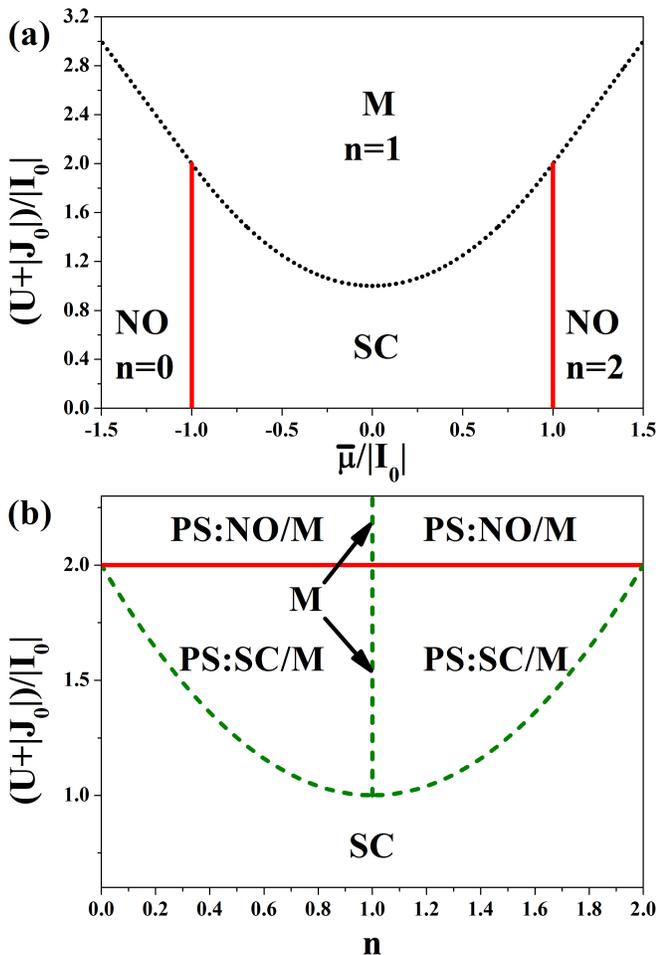


FIG. 2. Ground state diagram for $W = 0$ and $J \neq 0$ as a function of μ (a) and as a function of n (b). Denotations are the same as in Fig. 1. Details in text.

III. SUMMARY AND FINAL COMMENTS

The analysis of the model considered shows that the superconductivity can coexist with magnetism only in the state with phase separation (PS:SC/M for $1 < (U + |J_0|)/|I_0| < 2$, $W = 0$), whereas superconductivity and charge orderings — in the state with phase separation (PS:SC/CO) as well as in homogeneous mixed II phase (for $U < 0$, $W/|I_0| > 1$ and $J^z, J^{xy} = 0$). These last mentioned two states are degenerated at $T = 0$. This degeneration can be removed in the presence of long-range (at least between next-nearest neighbors) interactions [32].

The mixed homogeneous phases I2 (coexistence of SC and M orderings) does not appear on the phase diagrams.

Let us discuss how the properties of the system in the PS states evolve with n . If the SC fraction of the system is rather large (as it occurs near the boundary with the homogeneous SC phase, i.e. for $n \gtrsim n_{SC}$), for example, the measured penetration depth will remain constant with increasing n (since $n_- = n_{SC}$ is independent of n) [8, 31, 32]. On the other hand, near half-filling ($n \approx 1$) the SC fraction is strongly reduced and there will be only diluted SC domains (with $n_{SC} < 1$) in an insulating or semiconducting CO/M background (with $n_{CO/F} = 1$). When the SC domains do not percolate one should observe a partial Meissner effect but without zero resistance. In contrary, in the homogeneous mixed phases (I1, I2) behaviour of the SC characteristics would be totally different, because the whole system exhibits superconductivity and all of its SC properties (in particular, a penetration depth) would change with n , but with a full Meissner effect and zero resistance [37–39].

Notice that the results of Section II A together with results of [13, 32, 37, 43–46] give the full picture of behavior of model (1) for $U \leq 0$, $W \neq 0$, and $J^z, J^{xy} = 0$ within VA approach. A cases of $U > 0$ as well as $J^z, J^{xy} \neq 0$ are left to future works. Some analyses concerning the interplay between W and J^z, J^{xy} interactions for $I = 0$ have been performed in [5, 47–49].

ACKNOWLEDGMENTS

The author is indebted to Professor Stanisław Robaszkiewicz and Professor Roman Micnas for very fruitful discussions during this work and careful reading of the manuscript. The work has been financed by National Science Center (NCN, Poland) as a research project in the years 2011-2013, under Grant No. DEC-2011/01/N/ST3/00413. We thank the European Commission and the Ministry of Science and Higher Education (Poland) for the partial financial support from the European Social Fund—Operational Programme “Human Capital”—POKL.04.01.01-00-133/09-00—“Proinnowacyjne kształcenie, kompetentna kadra, absolwenci przyszłości”. We also thanks NCN for the doctoral scholarship No. DEC-2013/08/T/ST3/00012 in years 2013-2015 and the Foundation of Adam Mickiewicz University in Poznań for the support from its scholarship programme.

-
- [1] Johnston, D.C.: The puzzle of high temperature superconductivity in layered iron pnictides and chalcogenides. *Adv. in Physics* **59**, 803 (2010). doi:10.1080/00018732.2010.513480
- [2] Dagotto, E., Hotta, T., Moreo, A.: Colossal magnetore-

- sistant materials: The key role of phase separation. *Phys. Rep.* **334**, 1 (2001). doi:10.1016/S0370-1573(00)00121-6
- [3] Micnas, R., Robaszkiewicz, S., Bussman-Holder, A.: Two-component scenarios for nonconventional (exotic) superconductors. *Structure and Bonding* **114**, 13 (2005).

- doi:10.1007/b101016
- [4] Micnas, R., Ranninger, J., Robaszkiewicz, S.: Superconductivity in narrow-band systems with local nonretarded attractive interactions. *Rev. Mod. Phys.* **62**, 113 (1990). doi:10.1088/0022-3719/21/6/009
- [5] Robaszkiewicz, S.: Magnetism and charge ordering in the localized state. *Phys. Status Solidi (b)* **70**, K51 (1975). doi:10.1002/pssb.2220700156
- [6] Robaszkiewicz, S.: Pseudospin models of superconductors with very short coherence length. *Acta Phys. Pol. A* **85**, 117 (1994)
- [7] Robaszkiewicz, S., Pawłowski, G.: Effects of finite pair binding energy in a model of a superconductor with local electron pairing. *Physica C* **210**, 61 (1993). doi:10.1016/0921-4534(93)90009-F
- [8] Kapcia, K., Robaszkiewicz, S., Micnas, R.: Phase separation in a lattice model of a superconductor with pair hopping. *J. Phys.: Condens. Matter* **24**, 215601 (2012). doi:10.1088/0953-8984/24/21/215601
- [9] Kapcia, K., Robaszkiewicz, S.: The magnetic field induced phase separation in a model of a superconductor with local electron pairing. *J. Phys.: Condens. Matter* **25**, 065603 (2013). doi:10.1088/0953-8984/25/6/065603
- [10] Kapcia, K.: Metastability and phase separation in a simple model of a superconductor with extremely short coherence length. *J. Supercond. Nov. Magn.* **27**, 913 (2014). doi:10.1007/s10948-013-2409-8
- [11] Kapcia, K.J.: Superconductivity, metastability and magnetic field induced phase separation in the atomic limit of the Penson-Kolb-Hubbard model. *Acta Phys. Pol. A* **126**, A-53 (2014). doi:10.12693/APhysPolA.126.A-53
- [12] Kapcia, K.: Some properties of the model of a superconductor with pair hopping and magnetic interactions at half-filling. *Acta Phys. Pol. A* **121**, 733 (2012)
- [13] Kapcia, K.: Interplay and competition between superconductivity and charge orderings in the zero-bandwidth limit of the extended Hubbard model with pair hopping and on-site attraction. *J. Supercond. Nov. Magn.* **26**, 2647 (2013). doi:10.1007/s10948-013-2152-1
- [14] Kapcia, K.J.: Uporządkowania elektronowe i ich separacje w rozszerzonych modelach Hubbarda (in Polish). PhD thesis, Adam Mickiewicz University in Poznań, Poznań, March 2014 (2014). Accessed 6 December 2014. <http://hdl.handle.net/10593/10857>
- [15] Bari, R.A.: Superconductivity, ferroelectricity, and the Mott insulator. *Phys. Rev. B* **7**, 2128 (1973). doi:10.1103/PhysRevB.7.2128
- [16] Ho, W.-C., Barry, J.H.: Tricritical behavior and phase diagrams of the Bari model for Mott insulator-superconductor transitions. *Phys. Rev. B* **16**, 3172 (1977). doi:10.1103/PhysRevB.16.3172
- [17] Wiecko, C., Allub, R.: Superconductivity and random disorder in the zero-bandwidth limit. *Phys. Rev. B* **35**, 2041 (1987). doi:10.1103/PhysRevB.35.2041
- [18] Robaszkiewicz, S.: The charge-ordered state in an extended Hubbard model. *Phys. Status Solidi (b)* **59**, K63 (1973). doi:10.1002/pssb.2220590155
- [19] Micnas, R., Ranninger, J., Robaszkiewicz, S.: An extended Hubbard model with inter-site attraction in two dimensions and high-Tc superconductivity. *J. Phys. C: Solid State Phys.* **21**, L145 (1988). doi:10.1088/0022-3719/21/6/009
- [20] Hui, A., Doniach, S.: Penson-Kolb-Hubbard model: A study of the competition between single-particle and pair hopping in one dimension. *Phys. Rev. B* **48**, 2063 (1993). doi:10.1103/PhysRevB.48.2063
- [21] Robaszkiewicz, S., Bułka, B.: Superconductivity in the Hubbard model with pair hopping. *Phys. Rev. B* **59**, 6430 (1999). doi:10.1103/PhysRevB.59.6430
- [22] Ptok, A., Maška, M.M., Mierzejewski, M.: The Fulde-Ferrell-Larkin-Ovchinnikov phase in the presence of pair hopping interaction. *J. Phys.: Condens. Matter* **21**, 295601 (2009). doi:10.1088/0953-8984/21/29/295601
- [23] Ptok, A., Maška, M.M., Mierzejewski, M.: Coexistence of superconductivity and incommensurate magnetic order. *Phys. Rev. B* **84**, 094526 (2011). doi:10.1103/PhysRevB.84.094526
- [24] Czart, W.R., Robaszkiewicz, S.: Thermodynamic and electromagnetic properties of the Penson-Kolb model. *Phys. Rev. B* **64**, 104511 (2001). doi:10.1103/PhysRevB.64.104511
- [25] Robaszkiewicz, S., Czart, W.R.: Superconductivity in the two-dimensional extended Hubbard model with pair-hopping interaction. *Acta Phys. Pol. B* **32**, 3267 (2001)
- [26] Czart, W.R., Robaszkiewicz, S.: Superconducting properties of the η -pairing state in the Penson-Kolb-Hubbard model. *Acta Phys. Pol. A* **106**, 709 (2004)
- [27] Japaridze, G.I., Kampf, A.P., Sekania, M., Kakashvili, P., Brune, Ph.: η -pairing superconductivity in the Hubbard chain with pair hopping. *Phys. Rev. B* **65**, 014518 (2001). doi:10.1103/PhysRevB.65.014518
- [28] Dziurzik, C., Japaridze, G.I., Schadschneider, A., Zitzartz, J.: Triplet superconductivity vs. Easy-plane ferromagnetism in a 1D itinerant electron system with transverse spin anisotropy. *Eur. Phys. J. B* **37**, 453 (2004). doi:10.1140/epjb/e2004-00081-5
- [29] Czart, W.R., Robaszkiewicz, S.: Properties of the extended Hubbard model with transverse (XY-type) spin-exchange interaction. *Phys. Status Solidi (b)* **243**, 151 (2006). doi:10.1002/pssb.200562502
- [30] Czart, W.R., Robaszkiewicz, S.: Electron orderings of half-filled extended Hubbard models with spin-and charge-exchange interaction. *Acta Phys. Pol. A* **109**, 577 (2006)
- [31] Bąk, M.: Mixed phase and bound states in the phase diagram of the extended Hubbard model. *Acta Phys. Pol. A* **106**, 637 (2004)
- [32] Robaszkiewicz, S., Pawłowski, G.: Superconductivity, charge orderings and phase separations in systems with local electron pairing. *Acta Phys. Pol. A* **90**, 569 (1996)
- [33] Kapcia, K., Robaszkiewicz, S.: The effects of the next-nearest-neighbour density-density interaction in the atomic limit of the extended Hubbard model. *J. Phys.: Condens. Matter* **23**, 105601 (2011). doi:10.1088/0953-8984/23/10/105601
- [34] Kapcia, K., Robaszkiewicz, S.: The effects of the next-nearest-neighbour density-density interaction in the atomic limit of the extended Hubbard model. *J. Phys.: Condens. Matter* **23**, 249802 (2011). doi:10.1088/0953-8984/23/24/249802
- [35] Kapcia, K., Robaszkiewicz, S.: Stable and metastable phases in the atomic limit of the extended Hubbard model with intersite density-density interactions. *Acta Phys. Pol. A* **121**, 1029 (2012)
- [36] Kapcia, K., Kłobus, W., Robaszkiewicz, S.: Charge orderings and phase separations in the atomic limit of the extended Hubbard model with intersite density-density interactions. *Acta Phys. Pol. A* **118**, 350 (2010)

- [37] Robaszkiewicz, S., Micnas, R., Chao, K.A.: Thermodynamic properties of the extended Hubbard model with strong intra-atomic attraction and an arbitrary electron density. *Phys. Rev. B*, **23**, 1447 (1981). doi:10.1103/PhysRevB.23.1447
- [38] Micnas, R., Robaszkiewicz, S.: Thermodynamics of local-pair superconductors with anisotropic lattice structures. *Phys. Rev. B* **45**, 9900 (1992). doi:10.1103/PhysRevB.45.9900
- [39] Micnas, R., Robaszkiewicz, S., Kostyrko, T.: Thermodynamic and electromagnetic properties of hard-core charged bosons on a lattice. *Phys. Rev. B* **52**, 6863 (1995). doi:10.1103/PhysRevB.52.6863
- [40] Kłobus, W., Kapcia, K., Robaszkiewicz, S.: Magnetic orderings and phase separations in the zero-bandwidth limit of the extended Hubbard model with intersite magnetic interactions. *Acta Phys. Pol. A* **118**, 353 (2010)
- [41] Murawski, S., Kapcia, K., Pawłowski, G., Robaszkiewicz, S.: On the phase diagram of the zero-bandwidth extended Hubbard model with intersite magnetic interactions for strong on-site repulsion limit. *Acta Phys. Pol. A* **121**, 1035 (2012)
- [42] Murawski, S., Kapcia, K.J., Pawłowski, G., Robaszkiewicz, S.: Some properties of two dimensional extended repulsive Hubbard model with intersite magnetic interactions — a Monte Carlo study. *Acta Phys. Pol. A* **126**, A-110 (2014). doi:10.12693/APhysPolA.126.A-110
- [43] Pawłowski, G., Robaszkiewicz, S.: Superconducting properties and phase separation effects in systems with local pairing. *Acta Phys. Pol. A* **91**, 409 (1997)
- [44] Gerisch, T., Rieckers, A.: Limiting Gibbs states and phase transitions of a bipartite mean-field Hubbard model. *J. Stat. Phys.* **91**, 759 (1998). doi:10.1023/A:1023089930061
- [45] Gerisch, T., Münzner, R., Rieckers, A.: Canonical versus grand-canonical free energies and phase diagrams of a bipolaronic superconductor model. *J. Stat. Phys.* **91**, 1021 (1998). doi:10.1023/B:JOSS.0000033152.73539.a2
- [46] Bursill, R.J., Thompson, C.J.: Variational bounds for lattice fermion models II. Extended Hubbard model in the atomic limit. *J. Phys. A: Math. Gen.* **26**, 4497 (1993). doi:10.1088/0305-4470/26/18/017
- [47] Robaszkiewicz, S.: Magnetism and charge ordering in the Mott insulators. *Acta Phys. Pol. A* **55**, 453 (1979)
- [48] Kapcia, K., Kłobus, W., Robaszkiewicz, S.: Interplay between charge and magnetic orderings in the zero-bandwidth limit of the extended Hubbard model for strong on-site repulsion. *Acta Phys. Pol. A* **121**, 1032 (2012)
- [49] Mancini, F., Plekhanov, E., Sica, G.: Spin and charge orderings in the atomic limit of the U-V-J model. *J. Phys.: Conf. Series* **391**, 012148 (2012). doi:10.1088/1742-6596/391/1/012148